



Standard Terminology Relating to Methods of Mechanical Testing¹

This standard is issued under the fixed designation E 6; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope

1.1 This terminology covers the principal terms relating to methods of mechanical testing of solids. The general definitions are restricted and interpreted, when necessary, to make them particularly applicable and practicable for use in standards requiring or relating to mechanical tests. These definitions are published to encourage uniformity of terminology in product specifications.

1.2 Terms relating to fatigue and fracture testing are defined in Terminology E 1823.

2. Referenced Documents

2.1 *ASTM Standards:*²

E 8 Test Methods for Tension Testing of Metallic Materials

E 8M Test Methods for Tension Testing of Metallic Materials [Metric]

E 796 Test Method for Ductility Testing of Metallic Foil

E 1823 Terminology Relating to Fatigue and Fracture Testing

3. Index of Terms

3.1 The definitions of the following terms, which are listed alphabetically, appear in the indicated sections of 4.1.

Term	Section
accuracy	G
alignment	B
angle of bend	D
angle of twist	B
angular strain	see strain
axial strain	see strain
bearing area	F
bearing force	F
bearing strain	F
bearing strength	F

bearing stress	F
bearing yield strength	F
bend test	D
bending strain	see strain
bias, statistical	G
biaxial stretching	D
break elongation	see maximum elongation
breaking load	B
Brinell hardness number	C
Brinell hardness test	C
calibration	G
calibration factor	G
chord modulus	see modulus of elasticity
compressive strength	B
compressive stress	see stress
compressometer	G
constraint	A
creep	E
creep recovery	E
creep rupture strength	E
creep strength	E
deep drawing	D
deflectometer	G
direct verification	G
discontinuous yielding	B
discontinuous yielding stress	B
ductility	A
dynamic mechanical measurement	G
eccentricity	B
edge distance	F
edge distance ratio	F
elastic calibration device	G
elastic constants	see modulus of elasticity and Poisson's ratio
elastic force-measurement device	G
elastic limit	A
elastic modulus	see modulus of elasticity
elastic true strain	A
elongation	B
engineering strain	see strain
engineering stress	see stress
extensometer	G
extensometer system	G
fatigue ductility	D
fatigue ductility exponent	D
fatigue life	B
forming limit curve	D
forming limit diagram	D
fracture ductility	A
fracture strength	A
fracture stress	see stress
free bend	D
force	A
gage length	G
guided bend	D
hardness	C
indentation hardness	C

¹ This terminology is under the jurisdiction of ASTM Committee E28 on Mechanical Testing and is the direct responsibility of Subcommittee E28.91 on Editorial and Terminology except where designated otherwise. A subcommittee designation in parentheses following a definition indicates the subcommittee with responsibility for that definition.

Current edition approved April 1, 2006. Published April 2006. Originally approved 1923. Last previous edition approved 2003 as E 6 – 03^{ε1}.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

indirect verification G
 initial recovery E
 initial strain E
 initial stress E
 Knoop hardness number C
 Knoop hardness test C
 limiting dome height D
 linear (tensile or compressive) strain see **strain**
 load A
 lower yield strength B
 macrostrain see **strain**
 malleability see **ductility**
 mandrel (in bend testing) D
 maximum elongation B
 mechanical hysteresis A
 mechanical properties A
 mechanical testing A
 microstrain see **strain**
 modulus of elasticity A
 modulus of rigidity see **modulus of elasticity**
 modulus of rupture in bending D
 modulus of rupture in torsion B
 necking B
 nominal stress see **stress**
 normal stress see **stress**
 physical properties see **mechanical properties**
 pin see **mandrel (in bend testing)**
 plastic true strain A
 plunger see **mandrel (in bend testing)**
 precision G
 primary force standard G
 principal stress see **stress**
 Poisson's ratio A
 proportional limit A
 radius of bend D
 rate of creep E
 reduction of area E
 relaxation rate B
 relaxed stress E
 remaining stress E
 residual strain see **strain**
 residual stress see **stress**
 Rockwell hardness number C
 Rockwell hardness test C
 Rockwell superficial hardness number see **Rockwell hardness number**
 Rockwell superficial hardness test C
 semi-guided bend D
 Scleroscope hardness number C
 Scleroscope hardness test C
 secondary force standard G
 set A
 secant modulus see **modulus of elasticity**
 shear fracture B
 shear modulus A
 shear strain see **strain**
 shear strength B
 shear stress see **stress**
 slenderness ratio B
 static fatigue strength see **creep rupture strength**
 strain A
 strain gage fatigue life see **fatigue life**
 strain hardening A
 stress A
 stress relaxation E
 stress-rupture strength see **creep rupture strength**
 stress-strain diagram A
 tangent modulus see **modulus of elasticity**
 tensile strength B
 tensile stress see **stress**
 tension testing machine A
 testing machine A
 torque A
 torsional modulus see **modulus of elasticity**
 torsional stress see **stress**
 total elongation B
 transverse strain see **strain**

true strain see **strain**
 true stress see **stress**
 ultimate elongation see **maximum elongation**
 uniform elongation B
 upper yield strength B
 verification G
 Vickers hardness number C
 Vickers hardness test C
 wrap-around bend D
 yield point B
 yield point elongation B
 yield strength B
 B (also see **upper yield strength** and **lower yield strength**)
 Young's modulus A
 zero time E

4. Terminology

4.1 Terms and Definitions:

A. GENERAL DEFINITIONS

constraint, *n*—any restriction to the deformation of a body. (E28.11)

ductility, *n*—the ability of a material to deform plastically before fracturing. (E28.02)

DISCUSSION—Ductility is usually evaluated by measuring (1) the elongation or reduction of area from a tension test, (2) the depth of cup from a cupping test, (3) the radius or angle of bend from the bend test, or (4) the fatigue ductility from the fatigue ductility test (see Test Method E 796).

DISCUSSION—Malleability is the ability to deform plastically under repetitive compressive forces.

elastic limit [FL^{-2}], *n*—the greatest stress which a material is capable of sustaining without any permanent strain remaining upon complete release of the stress.

DISCUSSION—Due to practical considerations in determining the elastic limit, measurements of strain, using a small force rather than zero force, are usually taken as the initial and final reference.

fracture ductility, ϵ_f , *n*—the true plastic strain at fracture.

fracture strength, S_f [FL^{-2}], *n*—the normal stress at the beginning of fracture. Fracture strength is calculated from the force at the beginning of fracture during a tension test and the original cross-sectional area of the specimen.

force [F], *n*—in mechanical testing, a vector quantity of fundamental nature characterized by a magnitude, a direction, a sense, and a discrete point of application, that acts externally upon a test object and creates stresses in it. (E28.91)

DISCUSSION—Force is a derived unit of the SI system. Units of force in the SI system are newtons (N).

DISCUSSION—Where applicable, the noun **force** is preferred to **load** in terminology for mechanical testing.

least count, *n*—the smallest change in indication that can customarily be determined and reported.

DISCUSSION—In machines with close graduations it may be the value of a graduation interval; with open graduations or with magnifiers for reading, it may be an estimated fraction, rarely as fine as one tenth, of a graduated interval; and with verniers it is customarily the difference between the scale and vernier graduation measured in terms of scale units. If the indicating mechanism includes a stepped detent, the detent action may determine the least count.

load [F], *n*—in mechanical testing, an external force or system of forces or pressures, or both, that act upon the test object. (E28.91)

DISCUSSION—**Load** is a deprecated term and, where applicable, it should be replaced by **force**, particularly where it is used as a noun. For reasons of editorial simplicity or traditional usage, replacement of **load** by **force** may not always be desirable when used as a verb, adjective, or other part of speech (for example, to load a specimen, loading rate, load cell).

mechanical hysteresis, *n*—the energy absorbed in a complete cycle of loading and unloading. (E28.03)

DISCUSSION—A complete cycle of loading and unloading includes any stress cycle regardless of the mean stress or range of stress.

mechanical properties, *n*—those properties of a material that are associated with elastic and inelastic reaction when force is applied, or that involve the relationship between stress and strain.

DISCUSSION—These properties have often been referred to as “physical properties,” but the term “mechanical properties” is preferred.

mechanical testing, *n*—the determination of mechanical properties. (E28.90)

modulus of elasticity [FL⁻²], *n*—the ratio of stress to corresponding strain below the proportional limit.

DISCUSSION—The stress-strain relations of many materials do not conform to Hooke’s law throughout the elastic range, but deviate therefrom even at stresses well below the elastic limit. For such materials the slope of either the tangent to the stress-strain curve at the origin or at a low stress, the secant drawn from the origin to any specified point on the stress-strain curve, or the chord connecting any two specified points on the stress-strain curve is usually taken to be the “modulus of elasticity.” In these cases the modulus should be designated as the “tangent modulus,” the “secant modulus,” or the “chord modulus,” and the point or points on the stress-strain curve described. Thus, for materials where the stress-strain relationship is curvilinear rather than linear, one of the four following terms may be used:

(a) *initial tangent modulus* [FL⁻²], *n*—the slope of the stress-strain curve at the origin.

(b) *tangent modulus* [FL⁻²], *n*—the slope of the stress-strain curve at any specified stress or strain.

(c) *secant modulus* [FL⁻²], *n*—the slope of the secant drawn from the origin to any specified point on the stress-strain curve.

(d) *chord modulus* [FL⁻²], *n*—the slope of the chord drawn between any two specified points on the stress-strain curve below the elastic limit of the material. (E28.03)

DISCUSSION—Modulus of elasticity, like stress, is expressed in force per unit of area (pounds per square inch, etc.).

Poisson’s ratio, μ , *n*—the negative of the ratio of transverse strain to the corresponding axial strain resulting from an axial stress below the proportional limit of the material. (E28.03)

DISCUSSION—Poisson’s ratio may be negative for some materials, for example, a tensile transverse strain will result from a tensile axial strain.

DISCUSSION—Poisson’s ratio will have more than one value if the material is not isotropic.

proportional limit [FL⁻²], *n*—the greatest stress which a material is capable of sustaining without any deviation from proportionality of stress to strain (Hooke’s law).

DISCUSSION—Many experiments have shown that values observed for the proportional limit vary greatly with the sensitivity and accuracy of the testing equipment, eccentricity of loading, the scale to which the stress-strain diagram is plotted, and other factors. When determination of proportional limit is required, the procedure and the sensitivity of the test equipment should be specified.

set, *n*—strain remaining after complete release of the force producing the deformation.

DISCUSSION—Due to practical considerations, such as distortion in the specimen and slack in the strain indicating system, measurements of strain at a small force rather than zero force are often taken.

DISCUSSION—Set is often referred to as permanent set if it shows no further change with time. Time elapsing between removal of force and final reading of set should be stated.

shear modulus, *G* [FL⁻²], *n*—the ratio of shear stress to corresponding shear strain below the proportional limit, also called *torsional modulus* and *modulus of rigidity*. (E28.03)

DISCUSSION—The value of the shear modulus may depend on the direction in which it is measured if the material is not isotropic. Wood, many plastics and certain metals are markedly anisotropic. Deviations from isotropy should be suspected if the shear modulus differs from that determined by substituting independently measured values of Young’s modulus, *E*, and Poisson’s ratio, μ , in the relation:

$$G = E/[2(1 + \mu)]$$

DISCUSSION—In general, it is advisable in reporting values of shear modulus to state the range of stress over which it is measured.

strain, *e*, *n*—the per unit change, due to force, in the size or shape of a body referred to its original size or shape. Strain is a nondimensional quantity, but it is frequently expressed in inches per inch, metres per metre, or percent.

DISCUSSION—In this standard, “original” refers to dimensions or shape of cross section of specimens at the beginning of testing.

DISCUSSION—Strain at a point is defined by six components of strain: three linear components and three shear components referred to a set of coordinate axes.

DISCUSSION—In the usual tension, compression, or torsion test it is customary to measure only one component of strain and to refer to this as “the strain.” In a tension or a compression test this is usually the axial component.

DISCUSSION—Strain has an elastic and a plastic component. For small strains the plastic component can be imperceptibly small.

DISCUSSION—Linear thermal expansion, sometimes called “thermal strain,” and changes due to the effect of moisture are not to be considered strain in mechanical testing.

angular strain, *n*—use *shear strain*.

axial strain, *n*—linear strain in a plane parallel to the longitudinal axis of the specimen. (E28.04)

bending strain, *n*—the difference between the strain at the surface of the specimen and the axial strain. (E28.03, E28.10)

elastic true strain, ϵ_e , *n*—elastic component of the true strain.
engineering strain, *e*, *n*—a dimensionless value that is the change in length (ΔL) per unit length of original linear dimension (L_0) along the loading axis of the specimen; that is, $e = (\Delta L)/L_0$. (E28.02)

linear (tensile or compressive) strain, *n*—the change per unit length due to force in an original linear dimension. (E28.04)

DISCUSSION—An increase in length is considered positive.

macrostrain, n—the mean strain over any finite gage length of measurement large in comparison with interatomic distances. **(E28.13)**

DISCUSSION—Macrostrain can be measured by several methods, including electrical-resistance strain gages and mechanical or optical extensometers. Elastic macrostrain can be measured by X-ray diffraction.

DISCUSSION—When either of the terms *macrostrain* or *microstrain* is first used in a document, it is recommended that the physical dimension or the gage length, which indicate the size of the reference strain volume involved, be stated.

microstrain, n—the strain over a gage length comparable to interatomic distances. **(E28.13)**

DISCUSSION—These are the strains being averaged by the macrostrain measurement. Microstrain is not measurable by existing techniques. Variance of the microstrain distribution can, however, be measured by X-ray diffraction.

DISCUSSION—When either of the terms *macrostrain* or *microstrain* is first used in a document, it is recommended that the physical dimension or the gage length, which indicate the size of the reference strain volume involved, be stated.

plastic true strain, ϵ_p , n—the inelastic component of true strain.

residual strain, n—strain associated with residual stress. **(E28.13)**

DISCUSSION—Residual strains are elastic.

shear strain, n—the tangent of the angular change, due to force, between two lines originally perpendicular to each other through a point in a body. **(E28.04)**

transverse strain, n—linear strain in a plane perpendicular to the axis of the specimen.

DISCUSSION—Transverse strain may differ with direction in anisotropic materials.

true strain, ϵ , n—the natural logarithm of the ratio of instantaneous gage length, L , to the original gage length, L_0 ; that is, $\epsilon = \ln(L/L_0)$ or $\epsilon = \ln(1+e)$. **(E28.02)**

strain hardening, n—an increase in hardness and strength caused by plastic deformation. **(E28.02)**

stress [FL⁻²], n—the intensity at a point in a body of the forces or components of force that act on a given plane through the point. Stress is expressed in force per unit of area (for example, pounds-force per square inch, megapascals.).

DISCUSSION—As used in tension, compression, or shear tests prescribed in product specifications, stress is calculated on the basis of the original dimensions of the cross section of the specimen. This stress is sometimes called “engineering stress,” to emphasize the difference from true stress.

compressive stress [FL⁻²], n—normal stress due to forces directed toward the plane on which they act. **(E28.04)**

engineering stress, S [FL⁻²], n—the normal stress, expressed in units of applied force, F , per unit of original cross-sectional area, A_0 ; that is, $S = F/A_0$. **(E28.02)**

fracture stress [FL⁻²], n—the true normal stress on the minimum cross-sectional area at the beginning of fracture.

DISCUSSION—This term usually applies to tension tests of unnotched specimens.

nominal stress [FL⁻²], n—the stress at a point calculated on the net cross section by simple elastic theory without taking into account the effect on the stress produced by geometric discontinuities such as holes, grooves, fillets, and so forth.

normal stress [FL⁻²], n—the stress component perpendicular to a plane on which the forces act.

principal stress (normal) [FL⁻²], n—the maximum or minimum value of the normal stress at a point in a plane considered with respect to all possible orientations of the considered plane. On such principal planes the shear stress is zero.

DISCUSSION—There are three principal stresses on three mutually perpendicular planes. The states of stress at a point may be:

(1) *uniaxial* [FL⁻²], n —a state of stress in which two of the three principal stresses are zero,

(2) *biaxial* [FL⁻²], n —a state of stress in which only one of the three principal stresses is zero, or

(3) *triaxial* [FL⁻²], n —a state of stress in which none of the principal stresses is zero.

(4) *multiaxial* [FL⁻²], n —biaxial or triaxial.

residual stress [FL⁻²], n—stress in a body which is at rest and in equilibrium and at uniform temperature in the absence of external and mass forces. **(E28.13)**

shear stress [FL⁻²], n—the stress component tangential to the plane on which the forces act. **(E28.04)**

tensile stress [FL⁻²], n—normal stress due to forces directed away from the plane on which they act. **(E28.04)**

torsional stress [FL⁻²], n—the shear stress in a body, in a plane normal to the axis of rotation, resulting from the application of torque. **(E28.03)**

true stress, σ [FL⁻²], n—the instantaneous normal stress, calculated on the basis of the instantaneous cross-sectional area, A ; that is, $\sigma = F/A$; if no necking has occurred, $\sigma = S(1+e)$. **(E28.02)**

stress-strain diagram, n—a diagram in which corresponding values of stress and strain are plotted against each other. Values of stress are usually plotted as ordinates (vertically) and values of strain as abscissas (horizontally). **(E28.04)**

tension testing machine, CTR (constant rate of traverse), n—a mechanical device for applying a load (force) to a specimen and in which the force is measured by means of a pendulum. **(E28.01)**

testing machine (force-measuring type), n—a mechanical device for applying a force to a specimen. **(E28.01)**

torque [FL], n—a moment (of forces) that produces or tends to produce rotation or torsion. **(E28.03)**

Young’s modulus, E [FL⁻²], n—the ratio of tensile or compressive stress to corresponding strain below the proportional limit of the material. **(E28.03)**

B. TENSION, COMPRESSION, SHEAR, AND TORSION TESTING

alignment, n—the condition of a testing machine and load train (including the test specimen) that influences the introduction of bending moments into a specimen during tensile loading. **(E28.04)**

angle of twist (torsion test), n—the angle of relative rotation measured in a plane normal to the torsion specimen’s

longitudinal axis over the gage length. (E28.03)

breaking force [F], n —the force at which fracture occurs. (E28.04)

DISCUSSION—When used in connection with tension tests of thin materials or materials of small diameter for which it is often difficult to distinguish between the breaking force and the maximum force developed, the latter is considered to be the breaking force.

compressive strength [FL⁻²], n —the maximum compressive stress which a material is capable of sustaining. Compressive strength is calculated from the maximum force during a compression test and the original cross-sectional area of the specimen. (E28.04)

DISCUSSION—In the case of a material which fails in compression by a shattering fracture, the compressive strength has a very definite value. In the case of materials which do not fail in compression by a shattering fracture, the value obtained for compressive strength is an arbitrary value depending upon the degree of distortion which is regarded as indicating complete failure of the material.

discontinuous yielding, n —a hesitation or fluctuation of force observed at the onset of plastic deformation, due to localized yielding. (E28.04)

DISCUSSION—The stress-strain curve need not appear to be discontinuous.

discontinuous yielding stress, n —the peak stress at the initiation of the first measurable serration on the curve of stress-versus strain. (E28.10)

eccentricity, n —the distance between the line of action of the applied force and the axis of symmetry of the specimen in a plane perpendicular to the longitudinal axis of the specimen. (E28.04)

elongation, El , n —the increase in gage length of a body subjected to a tension force, referenced to a gage length on the body. Usually elongation is expressed as a percentage of the original gage length. (E28.04)

DISCUSSION—The increase in gage length may be determined either *at* or *after* fracture, as specified for the material under test.

DISCUSSION—The term elongation, when applied to metals, generally means measurement after fracture; when applied to plastics and elastomers, measurement at fracture. Such interpretation is usually applicable to values of elongation reported in the literature when no further qualification is given.

DISCUSSION—In reporting values of elongation the gage length shall be stated.

DISCUSSION—Elongation is affected by: specimen geometry; length, width, thickness of the gage section and adjacent regions; and test procedure, such as alignment and speed of pulling.

fatigue life, N_f , n —the numbers of cycles of stress or strain of a specified character that a given specimen sustains before failure of a specified nature occurs. (E28.04)

strain gage fatigue life, n —the number of fully reversed strain cycles corresponding to the onset of degraded gage performance, whether due to excessive zero shift or other detectable failure mode. (E28.14)

lower yield strength, LYS [FL⁻²], n —the minimum stress recorded during discontinuous yielding, ignoring transient effects. See Figs. 1 and 2. (E28.04)

maximum elongation, El_{max} , n —the elongation at the time of

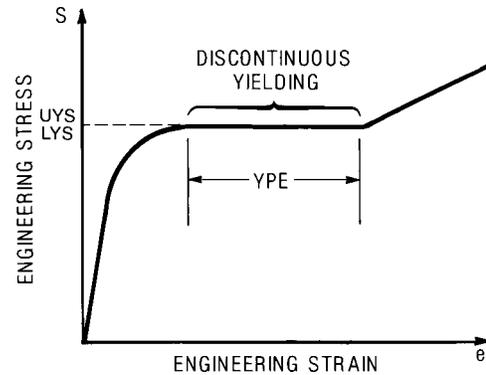


FIG. 1 Stress-Strain Diagram for Determination of Upper and Lower Yield Strengths and Yield Point Elongation in a Material Exhibiting Discontinuous Yielding

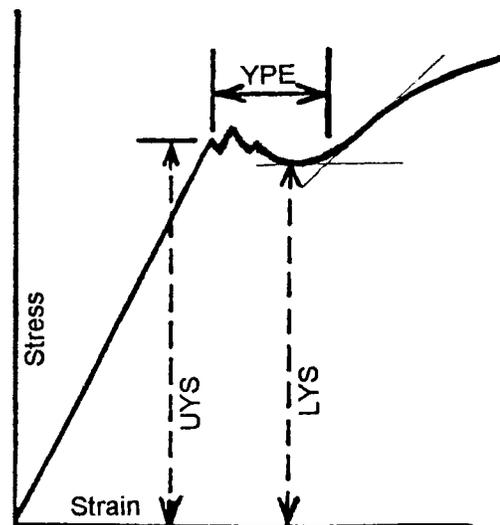


FIG. 2 Stress Strain Diagram Showing Yield Point Elongation and Upper and Lower Yield Strengths

fracture, including both elastic and plastic deformation of the tensile specimen. (E28.04)

DISCUSSION—This definition is used for rubber, plastic, and some metallic materials.

DISCUSSION—Maximum elongation is also called ultimate elongation or break elongation.

modulus of rupture in torsion [FL⁻²], n —the value of maximum shear stress in the extreme fiber of a member of circular cross section loaded to failure in torsion computed from the equation:

$$S_s = Tr/J \quad (1)$$

where:

T = maximum twisting moment,

r = original outer radius, and

J = polar moment of inertia of the original cross section. (E28.04)

DISCUSSION—When the proportional limit in shear is exceeded, the modulus of rupture in torsion is greater than the actual maximum shear stress in the extreme fiber, exclusive of the effect of stress concentration near points of application of torque.

DISCUSSION—If the criterion for failure is other than fracture or

attaining the first maximum of twisting moment, it should be so stated.

necking, n —the onset of nonuniform or localized plastic deformation, resulting in a localized reduction of cross-sectional area. (E28.02)

reduced section, n —the part of the specimen length between the fillets. (E28.04)

reduced section, n —section in the central portion of the specimen, which has a cross section smaller than the gripped ends. (E28.10)

reduction of area, n —the difference between the original cross-sectional area of a tension test specimen and the area of its smallest cross section. The reduction of area is usually expressed as a percentage of the original cross-sectional area of the specimen. (E28.04)

DISCUSSION—The smallest cross section may be measured at or after fracture as specified for the material under test.

DISCUSSION—The term reduction of area when applied to metals generally means measurement after fracture; when applied to plastics and elastomers, measurement at fracture. Such interpretation is usually applicable to values for reduction of area reported in the literature when no further qualification is given.

shear fracture, n —a mode of fracture in crystalline materials resulting from translation along slip planes which are preferentially oriented in the direction of the shearing stress. (E28.04)

shear strength $[FL^{-2}]$, n —the maximum shear stress which a material is capable of sustaining. Shear strength is calculated from the maximum force during a shear or torsion test and is based on the original dimensions of the cross section of the specimen. (E28.04)

slenderness ratio, n —the effective unsupported length of a uniform column divided by the least radius of gyration of the cross-sectional area. (E28.04)

tensile strength, S_u $[FL^{-2}]$, n —the maximum tensile stress which a material is capable of sustaining. Tensile strength is calculated from the maximum force during a tension test carried to rupture and the original cross-sectional area of the specimen. (E28.04)

total elongation, El_t , n —the elongation determined after fracture by realigning and fitting together of the broken ends of the specimen. (E28.04)

DISCUSSION—This definition is usually used for metallic materials.

uniform elongation, El_u $[\%]$, n —the elongation determined at the maximum force sustained by the test piece just prior to necking, or fracture, or both. (E28.04)

DISCUSSION—Uniform elongation includes both elastic and plastic elongation.

upper yield strength, UYS $[FL^{-2}]$, n —in a uniaxial test, the first stress maximum (stress at first zero slope) associated with discontinuous yielding at or near the onset of plastic deformation. See Fig. 1, Fig. 2, and Fig. 3 (E28.04)

yield point, YP $[FL^{-2}]$, n —term previously used, by E 8 and E 8M, for the property which is now referred to as **upper yield strength**. (E28.04)

yield point elongation, YPE , n —the strain (expressed in percent) separating the stress-strain curve's first point of zero

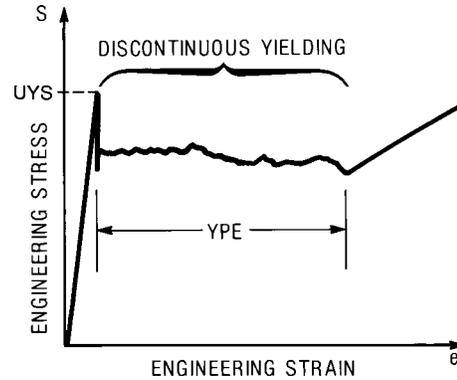


FIG. 3 Stress-Strain Diagram for Determination of Upper Yield Strength and Yield Point Elongation in a Material Exhibiting Discontinuous Yielding

slope from the point of transition from discontinuous yielding to uniform strain hardening. (E28.04)

DISCUSSION—If the transition occurs over a range of strain, the *YPE* end point is the intersection between (a) a horizontal line tangent to the curve at the last zero slope and (b) a line drawn tangent to the strain hardening portion of the stress-strain curve at the point of inflection. If there is no point at or near the onset of yielding at which the slope reaches zero, the material has 0% *YPE*.

yield strength, YS or S_y $[FL^{-2}]$, n —the engineering stress at which, by convention, it is considered that plastic elongation of the material has commenced. This stress may be specified in terms of (a) a specified deviation from a linear stress-strain relationship, (b) a specified total extension attained, or (c) maximum or minimum engineering stresses measured during discontinuous yielding. (E28.04)

DISCUSSION—The following types of yield strengths, which correspond to the approaches listed above may be specified:

(a) *specified offset yield strength, n* (usually an offset strain of 0.2 % is specified)—the engineering stress at which the material has been plastically strained by an amount equal to the specified offset strain. This stress is reached at the point where the stress-strain curve intersects a line having a slope equal to the modulus of elasticity and constructed such that it is offset from the linear portion of the stress-strain curve by an amount equal to the specified strain (see Fig. 4).

(b) *specified extension under load yield strength, n* (usually a strain of 0.5 % is specified, although higher strains may need to be used in testing of elastomers, polymers, and high-strength materials, to ensure that the yield strength determined will exceed the material's elastic limit)—the engineering stress at which the material has elongated (including both elastic and plastic deformation) an amount corresponding to the specified strain. This stress is attained at the point where the stress-strain curve intersects a line drawn parallel to the stress axis at the specified strain on the strain axis (see Fig. 5).

(c) *upper or lower yield strengths, n* —the upper (first maximum) or the lower (minimum, ignoring transient effects) engineering stress measured during discontinuous yielding occurring at or near the onset of plastic deformation (see Fig. 1, Fig. 2 and Fig. 3).

DISCUSSION—When yield strength is specified, the type of yield strength must be stated, along with the specified offset or extension under load, when applicable. The following are examples: *YS* (0.2 % offset), *YS* (0.5 % *EUL*), *UYS*, *LYS*.

DISCUSSION—Offset or extension under load yield strengths should be specified for continuously yielding materials, because upper and lower yield strengths are not defined for such materials. Determination of

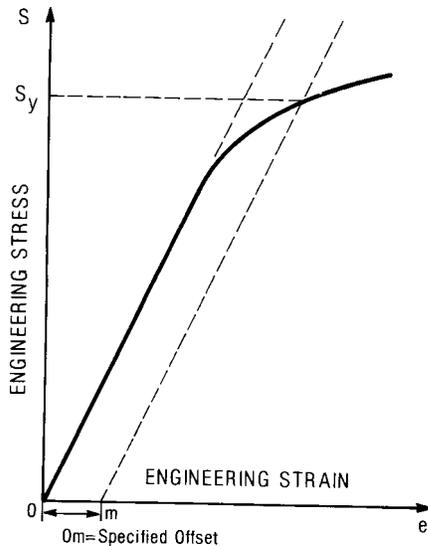


FIG. 4 Stress-Strain Diagram for Determination of Yield Strength by the Offset Method

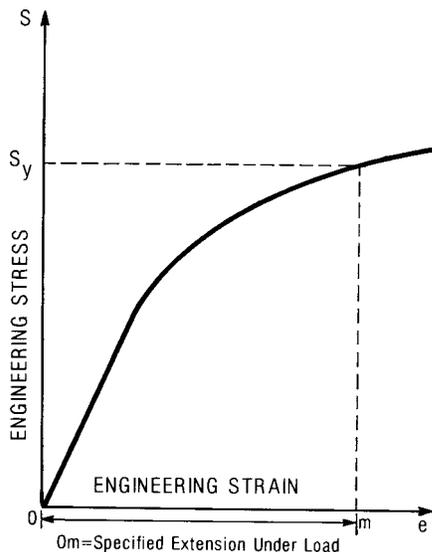


FIG. 5 Stress-Strain Diagram for Determination of Yield Strength by the Extension-Under-Load Method

upper or lower yield strengths, or both, is often favored for discontinuously yielding materials, because offsets or extensions constructed would generally intersect the portion of the stress-strain curve reflecting the stress oscillations which are characteristic of discontinuous yielding.

DISCUSSION—The values obtained by the methods described above may differ. However, when discontinuous yielding causes the stress-strain curve to show a stress hesitation with no pronounced increases or decreases (see Fig. 1), the offset, EUL and upper and lower yield strengths generally approach or attain a common value.

DISCUSSION—Yield strength, however determined, is generally affected by speed of testing. However, upper and lower yield strengths can also be dramatically influenced by test equipment parameters such as stiffness and alignment. (For more information, consult Appendix I of E 8 or E 8M.)

C. HARDNESS TESTING

Brinell hardness number, HB, *n*—indentation hardness test

in which a number proportional to the quotient obtained by dividing the test force by the curved surface area of the indentation which is assumed to be spherical and of the diameter of the ball.

$$HBW = 0.102 \times 2F / \pi D [D - (D^2 - d^2)^{-1/2}] \quad (2)$$

where:

F = test force, N,

D = diameter of ball, mm, and

d = mean diameter of the indentation, mm.

(E28.06)

DISCUSSION—In former standards, a steel ball was allowed for hardness values below 450. In cases where a steel ball was used the Brinell hardness was denoted by HB or HBS.

DISCUSSION—the symbol HBW is preceded by the hardness value when the test is carried out under the following conditions:

Ball diameter	10 mm
Force	3000 kgf
Duration of loading	10 to 15 s

When other conditions are used, the hardness value and symbol are supplemented by numbers indicating the test conditions in the following order: diameter of ball, force, and duration of loading.

Brinell hardness test, *n*—an indenter (tungsten carbide ball) is forced into the surface of a test piece and the diameter of the indentation left in the surface after removal of the test force is measured. (E28.06)

DISCUSSION—The tungsten carbide ball may be used for materials with Brinell hardness not exceeding 650.

hardness, *n*—the resistance of a material to deformation, particularly permanent deformation, indentation, or scratching. (E28.06)

DISCUSSION—Different methods of evaluating hardness give different ratings because they are measuring somewhat different quantities and characteristics of the material. There is no absolute scale for hardness; therefore, to express hardness quantitatively, each type of test has its own scale of arbitrarily defined hardness.

indentation hardness, *n*—the hardness as evaluated from measurements of area or depth of the indentation made by pressing a specified indenter into the surface of a material under specified static loading conditions. (E28.06)

Knoop hardness number, HK, *n*—a number related to the applied force and to the projected area of the permanent impression made by a rhombic-based pyramidal diamond indenter having included edge angles of 172° 30 min and 130° 0 min computed from the equation:

$$HK = P / 0.07028d^2 \quad (3)$$

where:

P = applied force, kgf, and

d = long diagonal of the impression, mm.

In reporting Knoop hardness numbers, the test force is stated. (E28.06)

Knoop hardness test, *n*—an indentation hardness test using calibrated machines to force a rhombic-based pyramidal diamond indenter having specified edge angles, under specified conditions, into the surface of the material under test and to measure the long diagonal after removal of the force.

fatigue ductility exponent, c , n —the slope of the log-log plot of the plastic strain range and the fatigue life. **(E28.04)**

forming limit curve, n —an empirically derived curve showing the biaxial strain levels beyond which localized through-thickness thinning (necking) and subsequent failure occur during the forming of a metallic sheet. **(E28.02)**

forming limit diagram, n —a graph on which the measured major and associated minor strain combinations are plotted to develop a forming limit curve. **(E28.02)**

free bend, n —the bend obtained by applying forces to the ends of a specimen without the application of force at the point of maximum bending. **(E28.02)**

DISCUSSION—In making a free bend, lateral forces first are applied to produce a small amount of bending at two points. The two bends, each a suitable distance from the center, are both in the same direction.

guided bend, n —the bend obtained by using a mandrel to guide and force the portion of the specimen being bent between two faces of a die. **(E28.02)**

limiting dome height (LDH)—an evaluative test for metal sheet forming capability employing a 200 mm (4in.) hemispherical punch and circumferential clamping force sufficient to prevent metal from the surrounding flange being pulled in the cavity. **(E28.02)**

mandrel (in bend testing), n —the tool used to control the strain on the concave side of a bend in a wrap-around bend test and also to apply the bending force in a semi-guided or guided bend test. **(E28.02)**

DISCUSSION—The terms “pin” and “plunger” have been used in place of mandrel.

DISCUSSION—In free bends or semi-guided bends to an angle of 180° a shim or block of the proper thickness may be placed between the legs of the specimen as bending is completed. This shim or block is also referred to as a pin or mandrel.

modulus of rupture in bending $[FL^{-2}]$, n —the value of maximum tensile or compressive stress (whichever causes failure) in the extreme fiber of a beam loaded to failure in bending computed from the flexure equation:

$$S_b = Mc/I \quad (5)$$

where:

- M = maximum bending moment, computed from the maximum force and the original moment arm,
- c = initial distance from the neutral axis to the extreme fiber where failure occurs, and
- I = initial moment of inertia of the cross section about the neutral axis.

(E28.02)

DISCUSSION—When the proportional limit in either tension or compression is exceeded, the modulus of rupture in bending is greater than the actual maximum tensile or compressive stress in the extreme fiber, exclusive of the effect of stress concentration near points of force application.

DISCUSSION—If the criterion for failure is other than rupture or attaining the first maximum force, it should be so stated.

radius of bend, n —the radius of the cylindrical surface of the pin or mandrel that comes in contact with the inside surface of the bend during bending. In the case of free or semi-guided bends to 180° in which a shim or block is used, the

radius of bend is one half the thickness of the shim or block. **(E28.02)**

semi-guided bend, n —the bend obtained by applying a force directly to the specimen in the portion that is to be bent. **(E28.02)**

DISCUSSION—The specimen is either held at one end or forced around a pin or rounded edge, or is supported near the ends and bent by a force applied on the side of the specimen opposite the supports and midway between them. In some instances, the bend is started in this manner and finished in the manner of the free bend.

wrap-around bend, n —the bend obtained when a specimen is wrapped in a closed helix around a cylindrical mandrel. **(E28.02)**

DISCUSSION—This term is sometimes applied to a semi-guided bend of 180° or less.

E. CREEP AND STRESS-RELAXATION TESTING

creep, n —the time-dependent increase in strain in a solid resulting from force. **(E28.10)**

DISCUSSION—Creep tests are usually made at constant load and at constant temperature. For tests on plastics the initial strain, however defined, is included and for metals it is not.

DISCUSSION—This change in strain is sometimes referred to as creep strain.

creep recovery, n —the time-dependent decrease in strain in a solid, following the removal of force. **(E28.10)**

DISCUSSION—Recovery is usually determined at constant temperature.

DISCUSSION—In tests of plastics, the initial recovery is generally included; for metals it is not. Thermal expansion is excluded.

creep rupture strength $[FL^{-2}]$, n —the stress that will cause fracture in a creep test at a given time, in a specified constant environment. **(E28.10)**

DISCUSSION—This is sometimes referred to as the *stress-rupture strength*. In glass technology this is termed the “static fatigue strength.”

creep strength $[FL^{-2}]$, n —the stress that causes a given creep in a creep test at a given time in a specified constant environment. **(E28.10)**

initial recovery, n —the decrease in strain in a specimen resulting from the removal of force, before creep recovery takes place. **(E28.10)**

DISCUSSION—This is sometimes referred to as instantaneous recovery.

DISCUSSION—Recovery is usually determined at constant temperature. Thermal expansion is excluded.

DISCUSSION—For tests on plastics, the initial recovery is generally included as part of creep recovery.

DISCUSSION—This definition describes a quantity which is difficult to measure accurately. The values obtained may vary greatly with the sensitivity and accuracy of the test equipment. When determining this quantity, the procedure and characteristics of the test equipment should be reported.

initial strain, n —the strain introduced into a specimen by the given loading conditions, before creep takes place. **(E28.10)**

DISCUSSION—This is sometimes referred to as instantaneous strain.

initial stress, n —the stress introduced into a specimen by imposing the given constraint conditions before stress relaxation begins. (E28.11)

DISCUSSION—This is sometimes referred to as instantaneous stress.

rate of creep, n —the slope of the creep-time curve at a given time. (E28.10)

relaxation rate, n —the absolute value of the slope of the relaxation curve at a given time. (E28.11)

DISCUSSION—A relaxation curve is a plot of either the remaining or relaxed stress as a function of time.

relaxed stress, n —the initial stress minus the remaining stress at a given time during a stress-relaxation test. (E28.11)

remaining stress, n —the stress remaining at a given time during a stress-relaxation test. (E28.11)

stress relaxation, n —the time-dependent decrease in stress in a solid under given constraint conditions. (E28.11)

DISCUSSION—The general stress relaxation test is performed by isothermally applying a force to a specimen with fixed value of constraint. The constraint is maintained constant and the constraining force is determined as a function of time.

zero time, n —the time when the given loading or constraint conditions are initially obtained in creep and stress-relaxation tests, respectively. (E28.10)

F. BEARING (PIN) TESTS

bearing area [L^2], n —the product of the pin diameter and specimen thickness. (E28.04)

bearing force [F], n —a compressive force on an interface. (E28.04)

bearing strain, n —the ratio of the bearing deformation of the bearing hole, in the direction of the applied force, to the pin diameter. (E28.04)

bearing strength [FL^{-2}], n —the maximum bearing stress which a material is capable of sustaining. (E28.04)

bearing stress [FL^{-2}], n —the force per unit of bearing area. (E28.04)

bearing yield strength [FL^{-2}], n —the bearing stress at which a material exhibits a specified limiting deviation from the proportionality of bearing stress to bearing strain. (E28.04)

edge distance [L], n —the distance from the edge of a bearing specimen to the center of the hole in the direction of applied force. (E28.04)

edge distance ratio, n —the ratio of the edge distance to the pin diameter. (E28.04)

G. MEASUREMENT AND CALIBRATION

accuracy, n —the permissible variation from the correct value. (E28.01)

bias, **statistical**, n —a constant or systematic error in test results. (E28.03)

calibration, n —a determination of the calibration factor for a system using established procedures. (E28.01)

calibration, n —determination of the values of the significant parameters by comparison with values indicated by a reference instrument or by a set of reference standards. (E28.06)

calibration factor, n —the factor by which the change in extensometer reading must be multiplied to obtain the equivalent strain. (E28.01)

DISCUSSION—For any extensometer, the calibration factor is equal to the ratio of change in length to the product of the gage length and the change in extensometer reading. For direct-reading extensometers the calibration factor is unity.

compressometer, n —a specialized extensometer used for sensing negative or compressive strain. (E28.01)

deflectometer, n —a specialized extensometer used for sensing of extension or motion, usually without reference to a specific gage length. (E28.01)

direct verification—verification that assesses fundamental parameters of the test or equipment, such as force, time, or dimensions. (See also **verification**).

dynamic mechanical measurement, n —a technique in which either the modulus or damping, or both, of a substance under oscillatory applied force or displacement is measured as a function of temperature, frequency, or time, or a combination thereof. (E28.03)

elastic calibration device, n —a device used in verifying the force readings of a testing machine consisting of an elastic member(s) to which forces may be applied, combined with a mechanism or device for indicating the magnitude (or a quantity proportional to the magnitude) of deformation of the member under an applied force. (E28.01)

elastic force measuring device, n —a device or system consisting of an elastic member combined with a device for indicating the magnitude (or a quantity proportional to the magnitude) of deformation of the member under an applied force. (E28.01)

extensometer, n —a device for sensing strain. (E28.01)

extensometer system, n —a system for sensing and indicating strain. (E28.01)

DISCUSSION—The system will normally include an extensometer, conditioning electronics, and auxiliary device (recorder, digital readout, computer, etc.). However, completely self-contained mechanical devices are permitted. An extensometer system may be one of three types.

Type 1 extensometer system, n —an extensometer system that both defines gage length and senses extension; for example, a clip-on strain gage type with conditioning electronics. (E28.01)

Type 2 extensometer system, n —an extensometer system that senses extension of a gage length that is defined by specimen features such as ridges, notches, or overall height (in case of a compression test piece). (E28.01)

DISCUSSION—The precision associated with gage length setting for a Type 2 extensometer should be specified in relevant test method or product standard. The position readout on a testing machine is not recommended for use in a Type 2 extensometer system.

Type 3 extensometer system, n —an extensometer system that intrinsically senses strain (ratiometric principle); for example, video camera system. (E28.01)

gage length [L], n —the original length of that portion of the specimen over which strain or change of length is determined. (E28.10)

DISCUSSION—When sensing extension or motion with a gage length

that is predetermined by the specimen geometry or specific test method, then only resolution and strain error for the specified gage length should determine the class of the extensometer system.

gage length, n —the original distance between gage marks made on the specimen for determining elongation after fracture. (E28.01)

indirect verification—verification that does not assess fundamental parameters of the test or equipment but that instead uses reference standards to determine whether the instrument generates results meeting applicable requirements.

precision, n —the degree of mutual agreement among individual measurements made under prescribed like conditions. (E28.03)

primary force standard, n —a deadweight force applied directly without intervening mechanisms such as levers, hydraulic multipliers, or the like, whose mass has been determined by comparison with reference standards traceable to national standards of mass. (E28.01)

resistance strain gage bridge, n —a common Wheatstone bridge made up of strain gages used for the measurement of

small changes of resistance produced by a strain gage. (E28.14)

secondary force standard, n —an instrument or mechanism, the calibration of which has been established by comparison with primary force standards

verification, n —an evaluation generating evidence to indicate whether an instrument, material, reference standard or procedure conforms to applicable requirements. (See also **direct verification** and **indirect verification**.)

DISCUSSION—Outside of mechanical testing, “verification” may refer to any check done to determine conformance. Within mechanical testing, the checking involves comparison to values indicated by a reference instrument or standard(s), and the applicable requirements generally address the accuracy and precision of data determined through use of the item verified.

5. Keywords

5.1 abbreviations; bearing; bend; compression; creep; ductility; foil; hardness; mechanical; pin; relaxation; shear; specifications; stress; symbols; tension; terms; testing; torsion

APPENDIX

(Nonmandatory Information)

X1. SYMBOLS AND ABBREVIATIONS

X1.1 The following symbols and abbreviations are frequently used instead of or along with the terms covered by these definitions. For stress, the use of S with appropriate lower case subscripts is preferred for general purposes; for mathematical analysis the use of Greek symbols is generally preferred.³

A	area of cross section
c	distance from centroid to outermost fiber
D	diameter
d	diameter or diagonal
DPH	diamond pyramid hardness (use HV, Vickers hardness number)
E	modulus of elasticity in tension or compression
F	force
G	modulus of elasticity in shear
HB	Brinell hardness number
HK	Knoop hardness number
HR	Rockwell hardness number (requires scale designation)
HV	Vickers hardness number
I	moment of inertia
J	polar moment of inertia
L	length
M	bending moment
P	concentrated load

r	radius
S	nominal engineering stress, or
S	normal engineering stress
S_a	shear engineering stress
S_c	compressive engineering stress
S_{cy}	compressive yield strength
S_t	tensile engineering stress
S_u	tensile strength
S_y	yield strength
T	temperature, torque, or twisting moment
t	time
W	work or energy
w	force per unit distance or per unit area
wA	total distributed force for a given area
wL	total distributed force for a given length
YPE	yield point elongation
YS	yield strength
Z	section modulus ³
Δ	increment
δ	deviation
ϵ	true strain
γ	shear strain
μ	Poisson's ratio ⁴
σ	normal true stress, nominal true stress ⁵
σ_c	compressive true stress
σ_t	tensile true stress
τ	shear true stress
θ	angle of twist per unit length

³ Many handbooks use S for section modulus, but Z is preferred since S is so widely used for normal or nominal stress.

⁴ ν (nu) is preferred in applied mechanics.

⁵Symbol confusion could result when statistical treatments are involved.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).